



Queens Road, Penkhull, Stoke-on-Trent,
Staffordshire ST4 7LQ, United Kingdom

tel: +44 (0)845 026 0902

fax: +44 (0)1782 412331

email: enquiries@ceram.com

web: www.ceram.com

TEST REPORT

Mr Simon Pearson
Tersus Ltd
Challenge Court
Bishops Castle
Shropshire
Sy9 5DW

Client's Mark -
Your Reference Terrazo tiles
Date Received 24.09.08
Laboratory N° (086436)-29413
Date Tested 20.10.08-17.11.08
Date Issued 16.12.08

DETERMINATION OF FREEZE/THAW RESISTANCE WITH DE-ICING SALT

1. SAMPLES

3 of Terazzo tile product

2. TEST PROCEDURE

The three samples were tested for weathering resistance with de-icing salts in accordance with BSEN 13748-2- 2004 – 'Terrazzo tiles — Part 2: Terrazzo tiles for external use, clause 5.9

3. RESULTS

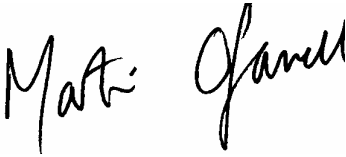
After 28 freeze thaw/de-icing salt cycles, any loose material scaled from the samples was rinsed from the test surface and filtered. The collected material was then weighed and the mass loss per unit area of the samples was calculated in kg/m².

Sample Number	Mass of Scaled Material (mg)	Area of Test Surface (mm ²)	Weight Loss (kg/m ²)
1	170	13406	0.01
2	3060	14327	0.21
3	4810	13677	0.35
			0.19

4. CONCLUSION

Table 5 of BSEN 13748-2 requires that the mean of the three blocks tested shall not be greater than 1.0kg/m², and no individual result to be greater than 1.5kg/m² in order for the blocks to be classed as 3, with a marking of D.

The sample of terrazzo tiles tested complies with this requirement.
(End of Test Report)

pp 

C.Mullington
Authorised Signatory